


This article was downloaded by: [Ramesh Malladi]

On: 07 August 2015, At: 20:48

Publisher: Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954 Registered office: 5 Howick Place, London, SW1P 1WG

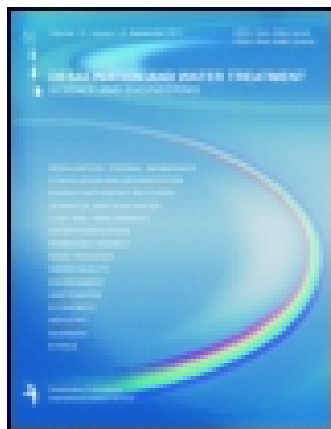

## Desalination and Water Treatment

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/tdwt20>

### Ag-TiO<sub>2</sub> nanoparticles for photocatalytic degradation of lomefloxacin

Raviraj M. Kulkarni<sup>a</sup>, Ramesh S. Malladi<sup>a</sup>, Manjunath S. Hanagadakar<sup>a</sup>, Mrityunjay R. Doddamani<sup>b</sup> & Udaya K. Bhat<sup>c</sup>

<sup>a</sup> Department of Chemistry, KLS Gogte Institute of Technology, (Affiliated to Visvesvaraya Technological University), Belagavi 590008, Karnataka, India, Tel. +91 8312498511; Fax: +91 8312441909

<sup>b</sup> Mechanical Engineering, National Institute of Technology Karnataka, Surathkal, India, Tel. +91 8242473678

<sup>c</sup> Metallurgical and Materials Engineering, National Institute of Technology Karnataka, Surathkal, India, Tel. +91 8242474000

Published online: 06 Aug 2015.



[Click for updates](#)

To cite this article: Raviraj M. Kulkarni, Ramesh S. Malladi, Manjunath S. Hanagadakar, Mrityunjay R. Doddamani & Udaya K. Bhat (2015): Ag-TiO<sub>2</sub> nanoparticles for photocatalytic degradation of lomefloxacin, *Desalination and Water Treatment*, DOI: [10.1080/19443994.2015.1076352](https://doi.org/10.1080/19443994.2015.1076352)

To link to this article: <http://dx.doi.org/10.1080/19443994.2015.1076352>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform. However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms & Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>



## Ag-TiO<sub>2</sub> nanoparticles for photocatalytic degradation of lomefloxacin

Raviraj M. Kulkarni<sup>a,\*</sup>, Ramesh S. Malladi<sup>a</sup>, Manjunath S. Hanagadakar<sup>a</sup>,  
Mrityunjay R. Doddamani<sup>b</sup>, Udaya K. Bhat<sup>c</sup>

<sup>a</sup>Department of Chemistry, KLS Gogte Institute of Technology, (Affiliated to Visvesvaraya Technological University), Belagavi 590008, Karnataka, India, Tel. +91 8312498511; Fax: +91 8312441909; emails: [ravirajmk@git.edu](mailto:ravirajmk@git.edu) (R.M. Kulkarni), [rameshmalladi7@gmail.com](mailto:rameshmalladi7@gmail.com) (R.S. Malladi), [manju.hanagadakar@gmail.com](mailto:manju.hanagadakar@gmail.com) (M.S. Hanagadakar)

<sup>b</sup>Mechanical Engineering, National Institute of Technology Karnataka, Surathkal, India, Tel. +91 8242473678; email: [Mrd1978@rediffmail.com](mailto:Mrd1978@rediffmail.com)

<sup>c</sup>Metallurgical and Materials Engineering, National Institute of Technology Karnataka, Surathkal, India, Tel. +91 8242474000; email: [udayabhatk@gmail.com](mailto:udayabhatk@gmail.com)

Received 5 January 2015; Accepted 21 July 2015

### ABSTRACT

The photocatalytic activity of silver-doped TiO<sub>2</sub> (Ag-TiO<sub>2</sub>) nanoparticles was studied by photocatalytic degradation of lomefloxacin (LMF) using a photoreactor with a mercury lamp (PHILIPS, TUV 8 W T5, E<sub>max</sub> = 254 nm). The 1 and 2% silver-doped TiO<sub>2</sub> nanoparticles were synthesized by liquid impregnation (LI) method. The resulting nanoparticles were characterized by surface analytical methods such as X-ray diffraction (XRD), scanning electron microscope (SEM), energy dispersive X-ray analysis and transmission electron microscope (TEM). The study shows 2% Ag-TiO<sub>2</sub> nanoparticles exhibited better results (95% degradation) in 1 h for the degradation of lomeofloxacin compared to 1% Ag-TiO<sub>2</sub> and pure TiO<sub>2</sub>. XRD analysis indicated that the crystallite size of TiO<sub>2</sub> was 17.00 nm, while the crystallite size of 1% Ag-TiO<sub>2</sub> and 2% Ag-TiO<sub>2</sub> was 13.07 to 14.17 nm. TEM images show the particle size of Ag-TiO<sub>2</sub> nanoparticles were in the range 40–45 nm in length and 10–15 nm in breadth. Pseudo-first-order rate constants were found to decrease with increase in pH. The effect of UV intensity, catalyst dosage and initial concentration of LMF on the degradation rate were also studied and elaborately discussed.

*Keywords:* Titanium dioxide; Liquid impregnation; Photocatalysis; Lomeofloxacin; AOP

### 1. Introduction

Advanced oxidation processes (AOPs) are techniques designed for the degradation of harmful organic contaminants which are resistant to conventional and biological treatment methods. AOPs depend on the generation of highly reactive radical species such as OH· that decompose a number of

organic contaminants without being selective [1–3] using chemical or light energy. The AOPs normally involve a semiconductor photocatalyst activated by UV or visible light resulting in partial or complete mineralization of the organic molecules [4,5].

There are several studies related to the use of TiO<sub>2</sub> in the photomineralization of pharmaceutical compounds [6,7].

Titanium dioxide (TiO<sub>2</sub>), a metal oxide semiconductor has been found to be one of the most

\*Corresponding author.

effective photocatalysts due to its chemical structure, biocompatibility, high efficiency low cost and optical and electrical properties [8,9].  $\text{TiO}_2$  has a band gap of 3.2 eV that allows UV light to excite the valance electrons into the conduction band leaving holes in the valance band [10]. The high rate of electron-hole recombination in  $\text{TiO}_2$ , however, limits the efficiency of the photocatalyst which can be prevented, to some extent, by doping with noble metals such as silver, gold, platinum [11]. The most important advantage of the doping of silver on  $\text{TiO}_2$  is improving the charge separation efficiency of the  $\text{TiO}_2$ . Moreover, the antibacterial action of silver, particularly in the colloidal form, is also well reported [12].

Lomefloxacin (LMF) is an antibacterial agent which belongs to the fluoroquinolone family, it is used to treat various bacterial infections, such as urinary tract, bronchitis etc. Now-a-days, antibacterial agents have been used in large amount for last few decades; these agents enter in to the environment through domestic sewage due to partial metabolism in the human body [13]. The chemical structure of LMF is given in Fig. 1.

However, no significant efforts have been made to investigate the detailed degradation kinetics, which is essential for the application point of view. Hence, we have carried out a detailed study on the photocatalytic degradation of LMF by Ag- $\text{TiO}_2$  nanoparticles in aqueous medium examining various reaction parameters such as pH, substrate and catalyst concentration, intensity of UV light. In the present work,  $\text{TiO}_2$  nanoparticles were doped with silver using liquid impregnation (LI) technique. These nanoparticles were characterized by the techniques such as X-ray diffraction (XRD), scanning electron microscope (SEM), energy dispersive X-ray analysis (EDX) and transmission electron microscope (TEM).

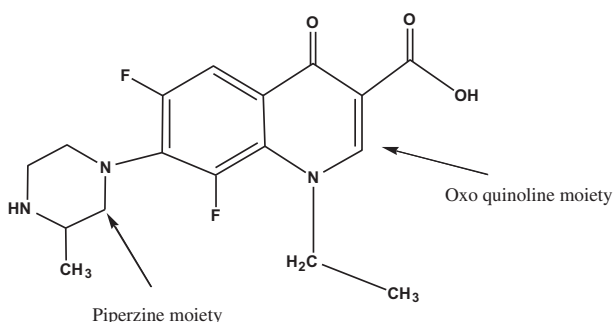


Fig. 1. Chemical structure of lomefloxacin.

## 2. Experimental

### 2.1. Materials and methods

A stock solution of LMF (Gift sample from Dr Reddy's laboratories) was prepared by dissolving appropriate amount of sample in double distilled water. The  $\text{TiO}_2$  sample was purchased from Sisco Research Pvt. Ltd, Mumbai 93, India ( $\text{TiO}_2$ -Anatase).  $\text{AgNO}_3$  purchased from HIMEDIA. The analytical grade chemicals were used to prepare acetate (pH 4–5), phosphate (pH 6.0–8.5) and borate (pH 9) buffers.

#### 2.1.1. Instruments used

- (1) For kinetic measurements, a CARY 50 Bio UV-vis spectrophotometer (Varian BV, The Netherlands) with temperature controller and HPLC system (Agilent 1100 series, USA) were used.
- (2) For degradation study, a photoreactor with mercury lamp (PHILIPS, TUV 8 W T5,  $E_{\text{max}} = 254 \text{ nm}$ ) was used. The typical light intensity illuminated on the surface of reaction mixture was  $4 \text{ mW/cm}^2$ .
- (3) For UV light intensity measurements, an optical power metre (Newport 2936-C) and for pH measurements, Elico pH metre models LI 120 were used.
- (4) For characterization of nanoparticles, a Siemens X-ray diffractometer (Cu source) (XRD) AXS D5005 was used to identify the particle size of the doped  $\text{TiO}_2$ . The surface morphologies were examined using a scanning electron microscope (SEM) JEOL JSM 6360.
- (5) The topography and particle size of Ag- $\text{TiO}_2$  was measured using JEOL JEM-2010 TEM.

### 2.2. Photo catalyst preparation

#### 2.2.1. LI method

500 mg of  $\text{TiO}_2$  was added to 100 ml deionized water in a 500 ml Pyrex beaker. For silver doping 1 and 2% (molar ratio) of  $\text{AgNO}_3$  was also added to the suspension. The resulting slurry was thoroughly mixed by vigorous stirring and allowed to settle at room temperature overnight. The liquid so obtained was dried in an oven at  $100^\circ\text{C}$  for 12 h to get rid of any remaining moisture. The solid material resulting from this step was calcined at  $500^\circ\text{C}$  for 3 h in a muffle furnace. This resulted in fine particles of Ag- $\text{TiO}_2$  nanoparticles [14,15].

### 2.3. The photocatalysis process

To investigate the photocatalytic degradation, a known concentration of LMF solution and buffer was taken in a Pyrex beaker. A dose of 100 mg/l 2% Ag-TiO<sub>2</sub> nanoparticles was added. Then, it was transferred in to the photoreactor and then kept under 8 W UV lamps (Philips) with a wavelength peak at 254 nm and of 4 mW/cm<sup>2</sup> intensity with continuous stirring. After every 15 min interval, the solution was taken out and centrifuged at 2,000 rpm for 5 min. The degradation of centrifuged solution was measured at 287 nm ( $\epsilon = 27,209 \text{ L M}^{-1} \text{ cm}^{-1}$ ) using visible spectrophotometer (a CARY 50 Bio UV-vis spectrophotometer (Varian BV, The Netherlands)) and the degree of mineralization was studied.

## 3. Results and discussion

### 3.1. Comparison of different photocatalysts

The rate of photo catalytic degradation of LMF with UV, UV/TiO<sub>2</sub>, UV/(1%) Ag-TiO<sub>2</sub> and UV/(2%) Ag-TiO<sub>2</sub> was studied. It is observed that the degradation effect of LMF treatment with UV/Ag-TiO<sub>2</sub> was more efficient than other two treatments namely UV and UV/TiO<sub>2</sub>.

Effect of silver doping on anatase TiO<sub>2</sub> was studied by changing the percentage of silver from 1 to 2% (mole ratio) an increase in the content of silver leads to decrease in the particle size and increase in the photocatalytic activity as shown in Fig. 2. Smaller particle size increases surface area and higher content silver may also favour separating charge carriers efficiently, inhibiting the recombination of electron-hole pairs, and thus increasing the photocatalytic activity

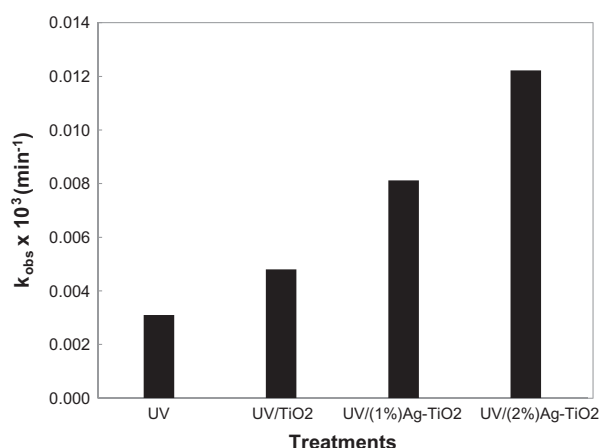


Fig. 2. Rate constants for the photocatalytic degradation of LMF by various treatments.

[16]. The photodegradation rate was highest with 2% Ag-TiO<sub>2</sub>; hence, further studies were carried out with 2% Ag-TiO<sub>2</sub>.

### 3.2. Characterization of TiO<sub>2</sub> and Ag-TiO<sub>2</sub>

The crystal phase of prepared nanoparticles was identified using X-ray diffractometer as shown in Fig. 3. The data indicates that the major phase of all the prepared nanoparticles is anatase. The average crystalline size of prepared nanoparticles was determined from the broadening of the anatase main intense peak (1 0 1), using Scherrer equation (1), which is shown in Table 1. Crystallite size of pure TiO<sub>2</sub> is of 17.00 nm, while the crystallite size of Ag-TiO<sub>2</sub> 1% is 14.17 nm, Ag-TiO<sub>2</sub> 2% 13.07. Our results are in accordance with earlier report [7], where Ag-TiO<sub>2</sub> nanoparticles dimensions were reported in between 15 and 37 nm.

$$D = \frac{0.94\lambda}{\beta_{1/2} \cos \theta} \quad (1)$$

where  $D$  is the average crystalline diameter,  $\lambda$  is the wavelength in angstrom,  $\beta$  is the line width at half-maximum and  $\theta$  is the Bragg angle.

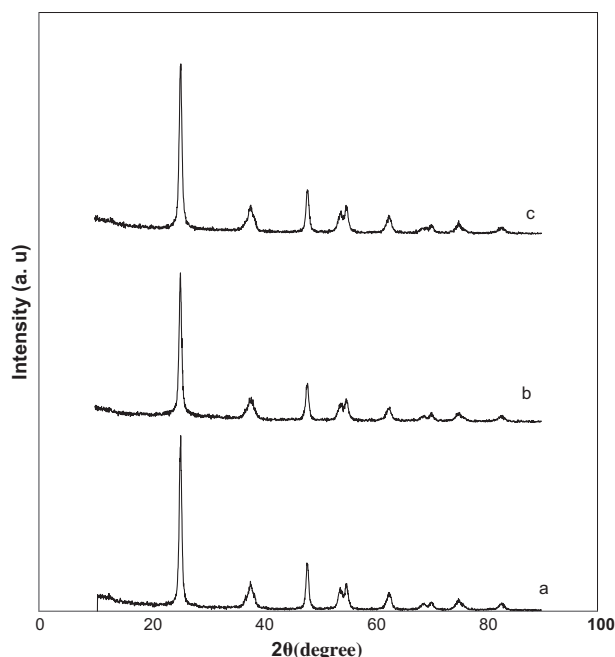


Fig. 3. XRD patterns of (a) undoped TiO<sub>2</sub>, (b) 1% and (c) 2% Ag-TiO<sub>2</sub>.

Table 1  
Crystal size of undoped and Ag doped TiO<sub>2</sub> nanoparticles from Scherrer equation

Sl. no.	Particles	Particle size (nm)
1	Un doped TiO <sub>2</sub>	17.00
2	1% Ag-TiO <sub>2</sub>	14.17
3	2% Ag-TiO <sub>2</sub>	13.07

### 3.3. Surface morphology study

#### 3.3.1. Scanning electron microscope

The SEM images have been used to characterize the size, shape and morphologies of formed nanoparticle clusters. It shows the non-uniform aggregates of the Ag-TiO<sub>2</sub> nanoparticles, which results in a high surface area. (Fig. 4(a)–(c)) represents the SEM images of the undoped and prepared Ag-TiO<sub>2</sub> nanoparticles [12].

#### 3.3.2. Transmission electron microscope

TEM images show the heterogeneously dispersed aggregates of Ag-TiO<sub>2</sub> nanoparticles having cylindrical shape crystalline structures which can be clearly observed in (Fig. 5(a) and (b)). Dispersion of small dark spots seen were presumed as Ag particles on TiO<sub>2</sub> nanoparticles with a particle size of approximately 10–15 nm in breadth and 40–45 nm in length. It is revealed that the crystallite size of the synthesized nanoparticles is close to that of TiO<sub>2</sub> nanoparticles obtained from XRD values.

#### 3.3.3. Electron diffraction X-ray spectroscopy

EDX examination provides information on chemical composition of samples. Fig. 6(a) and (b) shows that the prepared sample is mainly composed of Ti and O with small amount of Ag that increases with increase number of loading. Ag L peak was found, but peak of Ag K cannot be detected because low electron accelerating voltage was applied [17].

### 3.4. Effect of photocatalyst loading

To study the effect of catalyst loading, different amounts of catalyst were used from 50 to 250 mg/l while keeping [LMF] and pH 4 constant. It has been observed that initially the rate of photo degradation increases up to 100 mg/l, beyond 100 mg/l the rate of reaction almost constant (Fig. 7). This may be due to the fact that as the amount of semiconductor was increased in the initial state, the exposed surface area

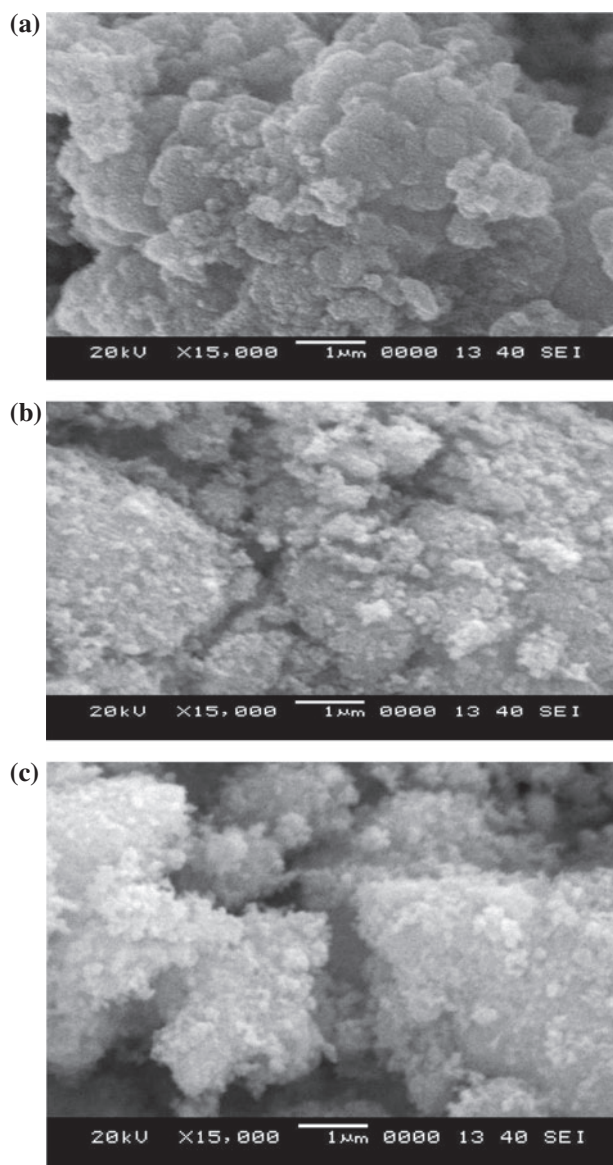


Fig. 4. SEM micrographs of (a) undoped TiO<sub>2</sub>, (b) 1% Ag-TiO<sub>2</sub> and (c) 2% Ag-TiO<sub>2</sub>.

of the semiconductor also increases, but after this limiting value (100 mg/l) any increase in the amount of semiconductor increases the turbidity of the solution and thus blocks UV irradiation for the reaction to proceed, and therefore degradation starts decreasing [18].

### 3.5. Effect of substrate concentration

The effect of variation of LMF concentration was studied by taking different concentration of LMF from  $8 \times 10^{-5}$  to  $28 \times 10^{-5}$  mol dm<sup>3</sup> by keeping other condition constant. It has been observed that with the initial

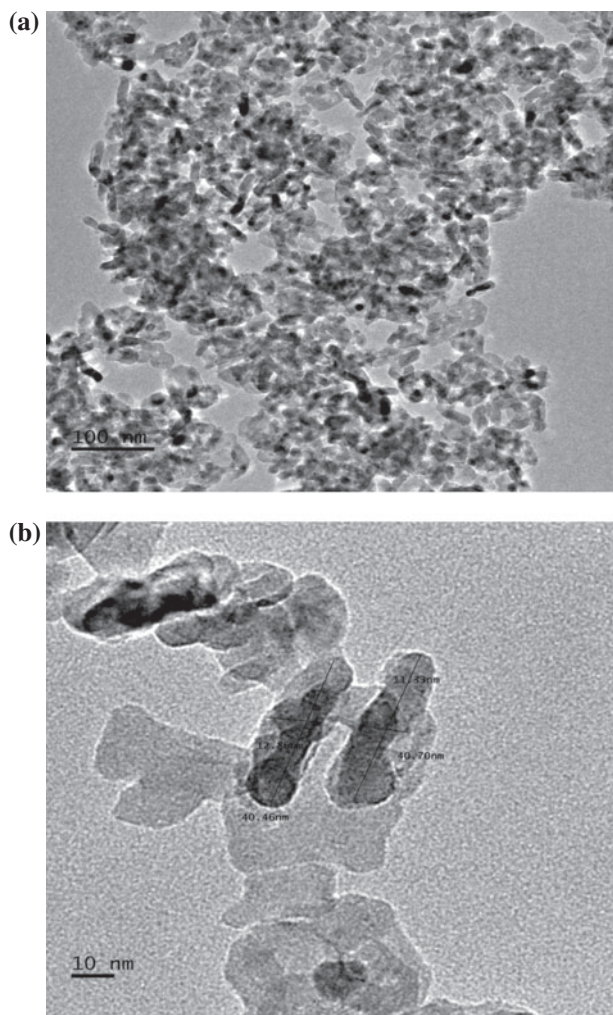


Fig. 5. TEM micrographs of 0.2% Ag/TiO<sub>2</sub>.

increase in the concentration of LMF, the rate of photocatalytic degradation increases, reaching maximum value [LMF] =  $20 \times 10^{-5}$  mol dm<sup>3</sup>; further increase in concentration resulted in decrease in the rate of photocatalytic degradation as shown in Fig. 8. It may be due to the fact that, as the concentration of the drug increased, more number of drug molecules are excited and consequently available for degradation, and hence the rate of degradation increases. But at concentration above  $20 \times 10^{-5}$  mol dm<sup>3</sup>, the drug itself acts as a filter for the incident light. This reduces the formation of OH<sup>-</sup> ions, due to which, the rate of photocatalytic degradation decreases [19].

### 3.6. Effect of pH

The pH normally influences the adsorption capacity of the adsorbent in aqueous medium by altering

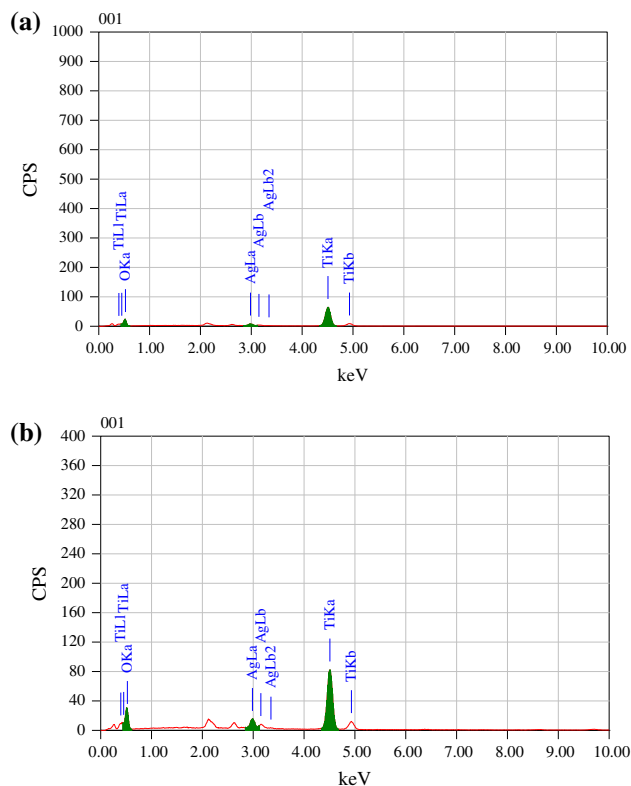


Fig. 6. (a) EDX analysis of 1% Ag-TiO<sub>2</sub> and (b) EDX analysis of 2% Ag-TiO<sub>2</sub>.

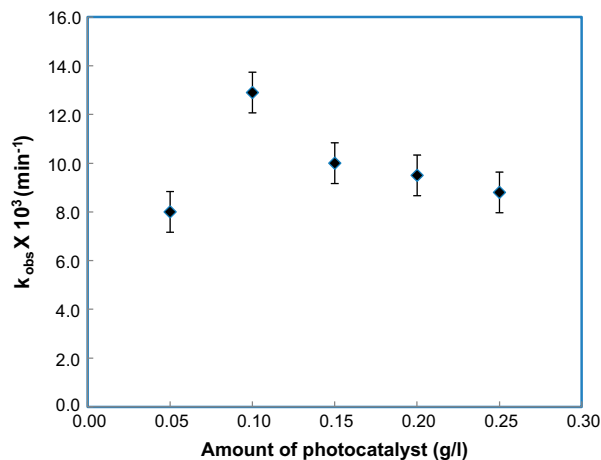


Fig. 7. Effect of different amounts of photocatalyst [LMF] =  $20 \times 10^{-5}$  M, at pH 4.

the surface properties of adsorbent. The effect of pH on the rate of photo degradation of LMF was studied by varying the pH from 4 to 8, while keeping other conditions constant. The rate of photocatalytic degradation of LMF was slightly higher in the pH

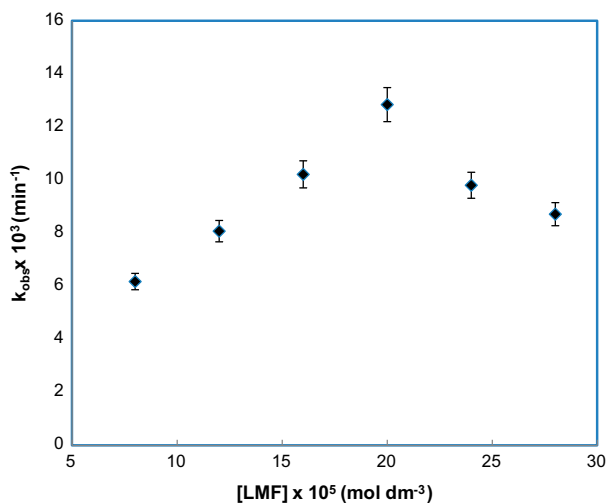


Fig. 8. Effect of variation of [LMF] on photocatalytic rate constants of photocatalytic process with 2% Ag-TiO<sub>2</sub> at 25 °C, [Ag-TiO<sub>2</sub>] = 100 mg/l, at pH 4.

range 4–5 and slightly lower in the pH range 7–8 as shown in Fig. 9. This behaviour may be explained on the basis that an increase in the rate of photocatalytic degradation may be due to the increased availability of OH<sup>-</sup> ions at acidic pH value. OH<sup>-</sup> ions will generate more hydroxyl radicals (·OH) by combining with holes, which are considered responsible for the photocatalytic degradation. The adsorption on Ag-TiO<sub>2</sub> primarily depends on its surface properties and surface

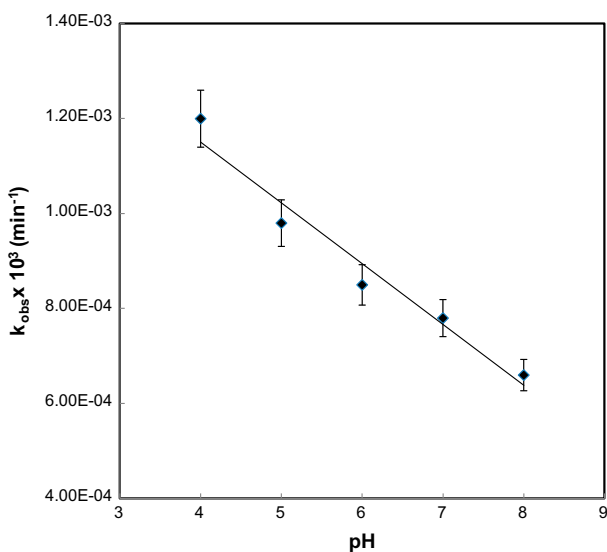


Fig. 9. Effect of pH on the rate constant of photocatalytic degradation of LMF with 2% Ag-TiO<sub>2</sub> at 25 °C, [Ag-TiO<sub>2</sub>] = 100 mg/l, [LMF] = 20 × 10<sup>-5</sup> M.

reactivity largely related to surface hydroxyl groups. It is evident from Table 2 that the adsorption capacity decreases with increase in the pH from 4 to 8. The LMF contains >NH and carboxyl functional groups in its molecular structure. This enables LMF to react with the H<sup>+</sup> and OH<sup>-</sup> in solution to form three different LMF species viz., LMFH<sup>+</sup> (cation), LMF<sup>0</sup> (neutral) and LMF<sup>-</sup> (anion). The pK<sub>a</sub> values of LMF were computed by using Chem axon calculator and they were found to be pK<sub>a1</sub> (5.64) and pK<sub>a2</sub> (8.7) [20]. The proportion of LMF in different forms can be calculated from the pK<sub>a</sub> values of LMF. The speciation pattern of LMF at different pH is shown in Fig. 10. LMF forms about 98% LMFH<sup>+</sup> at pH 4 by combining with H<sup>+</sup> ions from the solution, which favours the LMF adsorption on the negatively charged surface of Ag-TiO<sub>2</sub> photocatalyst. The proportion of LMFH<sup>+</sup> decreases to 81% at pH 5, reduces to 30% at pH 6 and further reduces to 4% (negligible) at pH 7. LMF neutral species dominates in the pH range 6–8. With the proportional decrease in the concentration of LMFH<sup>+</sup> and proportional increase in the concentration of LMF neutral, the adsorption capacity of LMF on Ag-TiO<sub>2</sub> decreases. The adsorption of LMFH<sup>+</sup> is due to the combination of cation with negatively charged surface of Ag-TiO<sub>2</sub>, whereas the adsorption of LMF neutral is due to weak Van der Waals forces of attraction. This observation is in line with the earlier report [21].

### 3.7. Effect of UV lamp distance

To examine the effects of UV light intensity on the degradation of lomefloxacin was studied by varying the distance of UV lamp from the target. The results are reported in Fig. 11. It is seen that an increase in light intensity increase the rate of photocatalytic degradation, and it is due to the fact that as the intensity increases the more number of Ag-TiO<sub>2</sub> nanoparticles excite to generate more electron hole pairs. The holes decompose the lomefloxacin molecules adsorbed on the surface of Ag-TiO<sub>2</sub> particles and oxidize it to water resulting in their efficient degradation [22].

### 3.8. Mechanism of photocatalytic degradation

On the basis of the experimental data the following tentative mechanism may be given for photocatalytic degradation of LMF.





Table 2  
Adsorption capacity at different pH (Langmuir isotherm)

Sl. no.	pH	Adsorption capacity (Langmuir isotherm) (mol/g)
1	4	0.00110
2	5	0.00091
3	6	0.00085
4	7	0.00072
5	8	0.00062

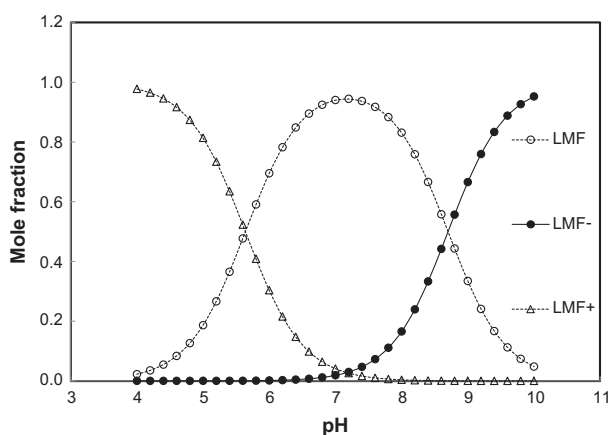


Fig. 10. Speciation of LMF at different pH.





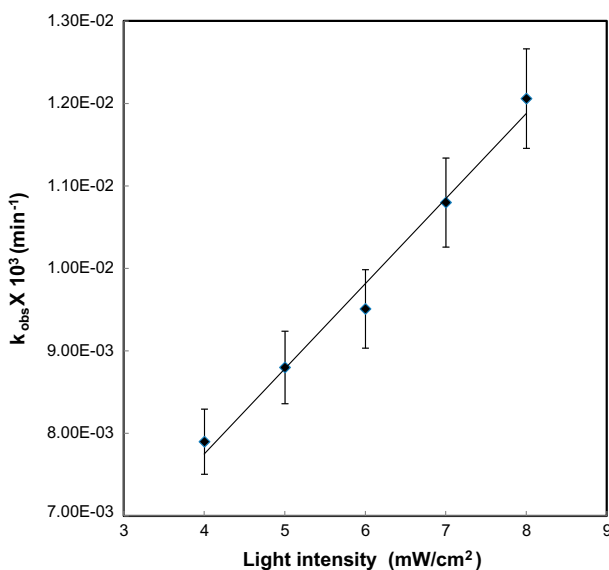


Fig. 11. LMF degradation under different UV intensities LMF with 2% Ag-TiO<sub>2</sub> at 25°C, [Ag-TiO<sub>2</sub>] = 100 mg l<sup>-1</sup>, [LMF] = 20 × 10<sup>-5</sup> M, at pH 4.



When the LMF solution is exposed to UV light, in the presence of Ag-TiO<sub>2</sub>, initially LMF molecules are excited to first singlet state (<sup>1</sup>LMF<sub>1</sub>). Then these excited molecules are moved to the triplet state through inter system crossing (ISC). The triplet drug (<sup>3</sup>LMF<sub>1</sub>) may provide its electron to the photocatalyst and become positively charged. The dissolved oxygen of the solution will pull an electron from the conduction band of the photocatalyst, thus generating the photocatalyst. The positively charged molecules of the drug (LMF) will immediately reacts with <sup>-</sup>OH ions to form OH<sup>·</sup> radicals, which will convert the drug molecules in to products.

In undoped TiO<sub>2</sub>, molecular oxygen is the only one electron trapping entity, whereas in Ag-TiO<sub>2</sub>, two other electron trapping entities are set up, viz., Ag<sup>+</sup> ions and Ag<sup>0</sup>. Since the Fermi level of TiO<sub>2</sub> is higher, hence electrons will move from TiO<sub>2</sub> nanoparticles to the metallic silver nanoparticles resulting in a space charge between Ag and TiO<sub>2</sub>. The electric field finally force the electrons to the interfacial space of the TiO<sub>2</sub> nanoparticles. Here, silver particles act as electron traps [23]. This leads to an increase in the charge separation efficiency and slows down electron-hole recombination. Silver metal on the catalyst surface improves the quantum yields by increasing the removal and the transfer of electrons from catalyst to molecular oxygen [24]. Therefore, molecular oxygen can trap photogenerated electrons to form superoxide radicals and consequently enhance the oxidation of LMF.

#### 4. Conclusion

1 and 2% silver doped TiO<sub>2</sub> nanoparticles were synthesized successfully by LI method. The XRD patterns of synthesized Ag-TiO<sub>2</sub> nanoparticles indicate anatase crystal structure. The EDX analysis and TEM topograph show the doping of silver in TiO<sub>2</sub>. In acidic environment at pH 4, the prepared Ag-TiO<sub>2</sub> nanoparticles (17.00–13.07 nm) exhibit good potential for the photocatalytic degradation of LMF. It is evident from the results that over 95% degradation of LMF could be achieved in 1 h using 2% Ag-TiO<sub>2</sub> photocatalyst.



## References

- [1] T. Kudo, Y. Nakamura, A. Ruike, The design of highly active rectangular column structured titanium oxide photocatalysts and their application in purification systems, *J. Catal. Today* 122 (2003) 14–19.
- [2] G. Zayani, L. Bousselmi, F. Mhenni, A. Ghrabi, Solar photocatalytic degradation of commercial textile azo dyes: Performance of pilot plant scale thin film fixed-bed reactor, *Desalination* 246 (2009) 344–352.
- [3] U.I. Gaya, A.H. Abdullah, Heterogeneous photocatalytic degradation of organic contaminants over titanium dioxide: A review of fundamentals, progress and problems, *J. Photochem. Photobiol. C* 9(1) (2008) 1–12.
- [4] C. Guillard, J. Disdier, J.M. Herrmann, C. Lehaut, T. Chopin, S. Malato, J. Blanco, Comparison of various titania samples of industrial origin in the solar photocatalytic detoxification of water containing 4-chlorophenol, *Catal. Today* 54 (1999) 217–228.
- [5] P. Bansal, N. Bhullar, D. Sud, Studies on photodegradation of malachite green using  $\text{TiO}_2/\text{ZnO}$  photocatalyst, *Desalin. Water Treat.* 12(1–3) (2009) 108–113.
- [6] A. Jodat, A. Jodat, Photocatalytic degradation of chloramphenicol and tartrazine using  $\text{Ag}/\text{TiO}_2$  nanoparticles, *Desalin. Water Treat.* 52(13–15) (2014) 2668–2677.
- [7] A. Verma, I.D. Chhikara Photocatalytic treatment of pharmaceutical industry wastewater over  $\text{TiO}_2$  using immersion well reactor: Synergistic effect coupling with ultrasound, *Desalin. Water Treat.* 52(34–36) (2014) 6591–6597.
- [8] Y. Yang, X.J. Li, J.T. Chen, L.Y. Wang, Effect of doping mode on the photocatalytic activities of  $\text{Mo}/\text{TiO}_2$ , *J. Photochem. Photobiol., A* 163(3) (2004) 517–522.
- [9] K.V. Baiju, C.P. Sibin, K. Rajesh, P.K. Pillai, P. Mukundan, K.G.K. Warriar, W. Wunderlich, An aqueous sol-gel route to synthesize nanosized lanthanadoped titania having an increased anatase phase stability for photocatalytic application, *Mater. Chem. Phys.* 90 (2005) 123–127.
- [10] C. Kormann, D.W. Bahnemann, M.R. Hoffmann, Preparation and characterization of quantum-size titanium dioxide, *J. Phys. Chem.* 92 (1988) 5196–5201.
- [11] M.S. Lee, S.S. Hong, M. Mohseni, Synthesis of photocatalytic nanosized  $\text{TiO}_2\text{-Ag}$  particles with sol-gel method using reduction agent, *J. Mol. Catal. A* 242 (2005) 135–140.
- [12] D. Guin, S.V. Manorama, J.N.L. Latha, S. Singh, Photoreduction of Silver on Bare and Colloidal  $\text{TiO}_2$  nanoparticles/nanotubes: Synthesis, characterization, and tested for antibacterial outcome, *J. Phys. Chem. C* 111 (2007) 13393–13397.
- [13] B. Halling-Sørensen, S.N. Nielsen, P.F. Lanzky, F. Ingerslev, H.C. Holten Lützhøft, S.E. Jørgensen, Occurrence, fate and effects of pharmaceutical substances in the environment—A review, *Chemosphere* 36(2) (1998) 357–393.
- [14] M.A. Behnajady, N. Modirshahla, M. Shokri, B. Rad, Enhancement of photocatalytic activity of  $\text{TiO}_2$  nanoparticles by silver doping: Photodeposition versus liquid impregnation methods, *Global NEST J.* 10(1) (2008) 1–7.
- [15] H. Ilyas, I.A. Qazi, W. Asgar, M.A. Awan, Z. Khan, Photocatalytic degradation of nitro and chlorophenols using doped and undoped titanium dioxide nanoparticles, *J. Nanomater.* 2011 (2011) 1–8.
- [16] U.S. Ozkan, M.W. Kumthekar, G. Karakas, Characterization and temperature-programmed studies over  $\text{Pd}/\text{TiO}_2$  catalysts for NO reduction with methane, *Catal. Today* 40(1) (1998) 3–14.
- [17] K. Wetchakun, S. Phanichphant, Effect of Ru on photocatalytic activity of  $\text{TiO}_2$  nanoparticles, *J. Microsc. Soc. Thailand* 22 (2008) 11–14.
- [18] J. Sun, L. Qiao, S. Sun, G. Wang, Photocatalytic degradation of Orange G on nitrogen-doped  $\text{TiO}_2$  catalysts under visible light and sunlight irradiation, *J. Hazard. Mater.* 155 (2008) 312–319.
- [19] C.C. Wang, C.K. Lee, M.D. Lyu, L.C. Juang, Photocatalytic degradation of C.I. Basic Violet using  $\text{TiO}_2$  catalysts supported by Y. Zeolite an investigation of the effects of operational parameters, *Dyes Pigm.* 76 (2008) 312–319.
- [20] Marvin 5.10.1, 2012, ChemAxon. Available from: <<http://www.chemaxon.com>>.
- [21] I.T. Horvath, Heterogeneous photocatalytic degradation of organic contaminants over titanium dioxide: A review of fundamentals, progress and problems, *J. Encycl. Catal.* 5 (2003) 577–599.
- [22] Z. Guo, R. Ma, G. Li, Degradation of phenol by nanomaterial  $\text{TiO}_2$  in wastewater, *Chem. Eng. J.* 119 (2006) 55–59.
- [23] C. He, Y. Yu, X. Hu, A. Larbot, Influence of silver doping on the photocatalytic activity of titania films, *Appl. Surf. Sci.* 200 (2002) 239–247.
- [24] H. Gerischer, A. Heller, Photocatalytic oxidation of organic molecules at  $\text{TiO}_2$  particles by sunlight in aerated water, *J. Electrochem. Soc.* 139 (1992) 113–118.